

Disponible en [www.hormigonyacero.com](http://www.hormigonyacero.com)  
Hormigón y Acero, 2023  
<https://doi.org/10.33586/hya.2023.3097>

## ARTÍCULO EN AVANCE ONLINE

### **Linear concrete tension stiffening model for reinforced concrete elements**

Luisa Hdz-Gil, Enrique Hernández-Montes

DOI: <https://doi.org/10.33586/hya.2023.3097>

Para ser publicado en: *Hormigón y Acero*

Por favor, el presente artículo debe ser citado así:

**Hdz-Gil, L., Hernández-Montes, E. (2023) Linear concrete tension stiffening model for reinforced concrete elements, *Hormigón y Acero*, <https://doi.org/10.33586/hya.2023.3097>**

Este es un archivo PDF de un artículo que ha sido objeto de mejoras propuestas por dos revisores después de la aceptación, como la adición de esta página de portada y metadatos, y el formato para su legibilidad, pero todavía no es la versión definitiva del artículo. Esta versión será sometida a un trabajo editorial adicional, y una revisión más antes de ser publicado en su formato final, pero presentamos esta versión para adelantar su disponibilidad.

En el proceso editorial y de producción posterior pueden producirse pequeñas modificaciones en su contenido.

© 2023 Publicado por CINTER Divulgación Técnica para la Asociación Española de Ingeniería Estructural, ACHE

# Linear concrete tension stiffening model for reinforced concrete elements

## Modelo lineal de la rigidez a tracción del hormigón para elementos de hormigón estructural

Luisa Hdz-Gil

School of Civil Engineers, University of Granada.  
Campus Universitario de Fuentenueva, E-18072 Granada. Spain. [luisahernandez@correo.ugr.es](mailto:luisahernandez@correo.ugr.es)

Enrique Hernández-Montes

Professor. School of Civil Engineers, University of Granada.  
Campus Universitario de Fuentenueva, E-18072 Granada. Spain. [emontes@ugr.es](mailto:emontes@ugr.es)

Keywords: tension stiffening of concrete; deflections of RC elements; concrete model

### Abstract

Nowadays, linear expressions for the tension stiffening of concrete are widely used in structural analysis software packages. Nevertheless, more complex expressions of tension stiffening available in the literature have been used successfully in the past. The use of linear approximations is justified since the influence of the tension stiffening effect on the deformation of a structure is small but not negligible. Therefore, linear approximations are simpler and can be accurate enough. However, the linear approximation, in its present form, does not provide good results in terms of deformations of reinforced concrete beam-column elements. This paper proposes a linear expression of tension stiffening supported by the experimental formulation used to predict the flexural behavior of concrete beams. A detailed example is presented.

### Resumen

Expresiones lineales de la rigidez a tracción del hormigón están siendo ampliamente utilizadas en paquetes de software de análisis estructural. Sin embargo, en el pasado se han utilizado con éxito expresiones más elaboradas de la rigidez a tracción del hormigón. El uso de aproximaciones lineales está justificado ya que la influencia del efecto de rigidez a tracción del hormigón en la deformación de las estructuras de hormigón es pequeña pero no despreciable. En este sentido, las aproximaciones lineales son más simples y pueden ser lo suficientemente precisas. Sin embargo, esta aproximación lineal, en su forma actual, no proporciona buenos resultados en términos de deformaciones a nivel de elementos estructurales. Esta publicación propone una expresión lineal de la rigidez a tracción apoyada por la formulación experimental utilizada para predecir el comportamiento a flexión de vigas de hormigón. Se presenta un ejemplo detallado.

## 1. Introduction

The phenomenon of concrete tensile contribution, for tensile strains greater than the cracking strain, is called tension stiffening of concrete. This contribution is caused by the bond effect between the concrete and the reinforcing bars. Comprehensive studies of this phenomenon can be found in [1], [2], [3], and [4]. Tension stiffening models have been widely used in the study of the shear response of both reinforced and prestressed concrete elements by using the two main theories: the MCFT (Modified Compression Field Theory [2]) and the RA-STM (Rotating Angle Softened Truss Model [3]). There are several discrepancies between these two main theories, which have been the subject of an exhaustive justification by other authors [5], [6].

International software for structural analysis, such as OpenSees [7] and Sap2000 [8], use approximated linear expressions for the tension stiffening model, e.g. model “Concrete02” of OpenSees. When using Concrete02, the post-cracking behavior in tension is described by a line that goes from the tensile strength to 0 in a constant slope which is usually deduced by assuming that the tension stiffening capacity is null at a value of the strain equal to the yield strain of steel ( $\epsilon_y$ ). See in the line between the points Fig.1:  $(-\epsilon_{ct}, -f_{ct})$  and  $(-\epsilon_y, 0)$ .

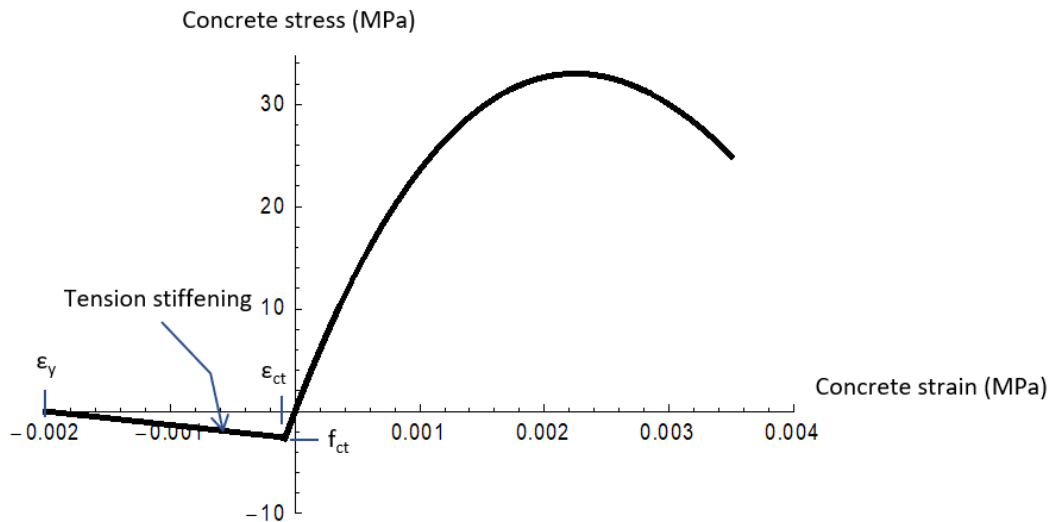


Figure 1. Strain-Stress curve of concrete, including tension stiffening.

However, as shown below, it has been found that the deflections calculated when using the model described in Fig. 1 are lower than those predicted by the formulations proposed by current regulations (EN 1992[9], ACI-318[10]), which are based on large experimental campaigns.

Considering that the tension stiffening effect is primarily caused by the bond mechanism between concrete and reinforcement [11], the premise that it is zero at  $\epsilon=\epsilon_y$  [1] is well established. Alternatively, some authors consider that small amount of tensile strength of concrete between cracks beyond yielding [12] remains, with a consequent increase in the rigidity of the RC element beyond the yielding of the reinforcement.

So, if tension stiffening is assumed to be zero at  $\epsilon=\epsilon_y$ , then the only variable that remains for modeling the tension stiffening effect is the tension strength of concrete,  $f_{ct}$ . In this paper, a  $\psi$  factor is introduced to adjust  $f_{ct}$  so that the theoretical deflection matches the result proposed by the current standards.

It is known that for tension strains larger (in absolute value) than the one that corresponds to cracking (note that cracking happens at  $(-\epsilon_{ct}, -f_{ct})$ , see Figure 1), the stress and strain distributions along the length of the reinforcing bars are no longer constant for either steel or concrete, see Figure 2, adapted from [11].

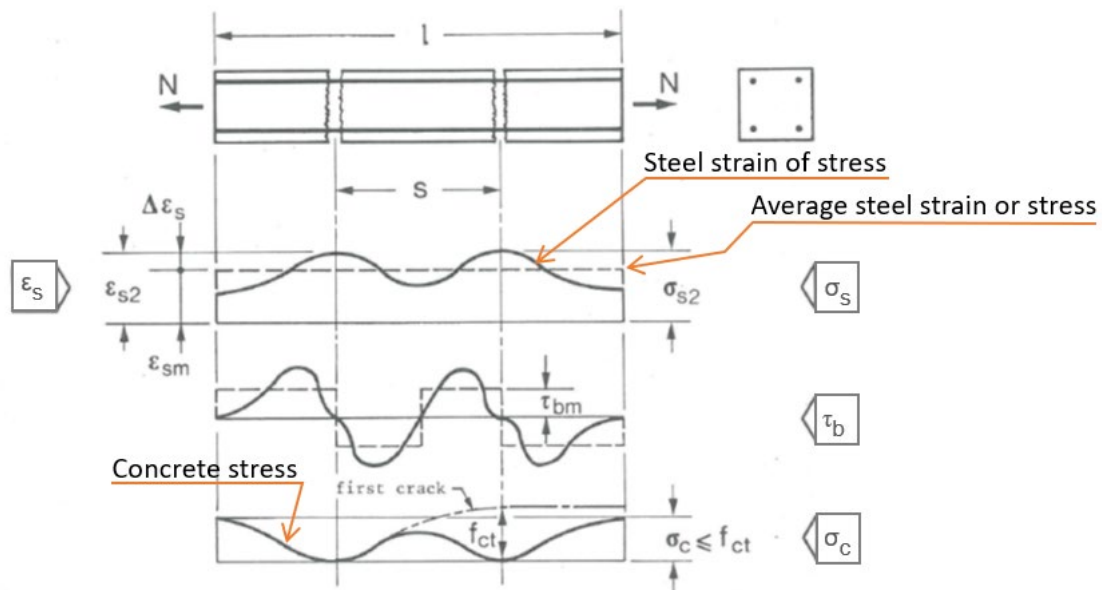


Figure 2. Stress and strain distributions along the reinforcing bars and the effective concrete area, adapted from [11].

Due to this variability, the strain of the bar could be  $\epsilon_y$  at the crack location while in sections between cracks (where concrete in tension is undamaged), the bar stress is lower than  $f_y$ . This implies that the average stress-strain response of the reinforcement exhibits yielding at an average stress that is below  $f_y$ . The average steel stress and strain associated with the yielding at a crack location is called “apparent yield” [3],[5], see Figure 3. Thus, before the average strain (i.e., calculated along a length intersecting several cracks) reaches  $\epsilon_y$ , the steel reinforcement will have already yielded at the cracks. Beyond the apparent yield point, the tension stiffening phenomenon presents a large drop in its slope [1],[11] which cannot be observed when using the linear approach, see Figure 3 adapted from [2]. This drawback can be overcome by appropriately correcting the value of the tensile strength of concrete, as proposed in this work.

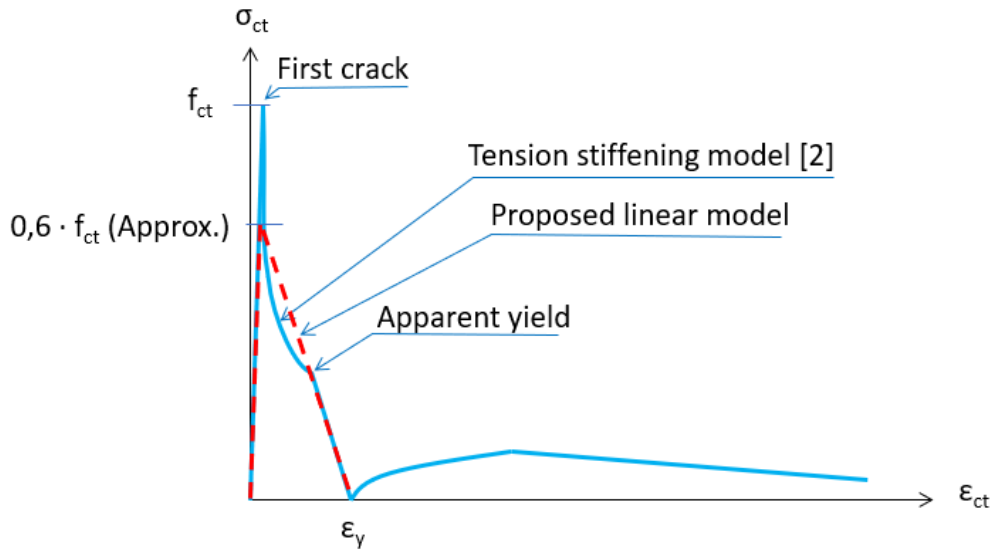


Figure 3. Variation of average tensile stress in concrete up to failure

## 2. Deflection formulation for beam elements

The linear tension stiffness model proposed is going to be evaluated using results from the deflections of beams. The deflections used in this study are obtained from formulations endorsed by ACI-318 and EN 1992, which represent the experience and approval of the engineering community.

ACI-318 uses an interpolation function to calculate effective inertia, [13], while EN 1992 uses an interpolation function that is applicable to the deflections calculated with the gross inertia and with the cracked inertia, [11]. Recently, slenderness limits have been proposed to avoid the explicit calculation of cracking and deformation. [14].

EN 1992 presents an explicit formulation of the concrete stress-strain curve, and therefore this study has been developed using the European code (e.g. Figure 1 shows the stress-strain formulation given by EN 1992 for a concrete with a characteristic strength of 25 MPa).

### Example

The example studied is a simply supported beam with a 6-meter span, which is of the beams used in the construction of buildings. This example, shown in Fig.4, has been adapted from [11].

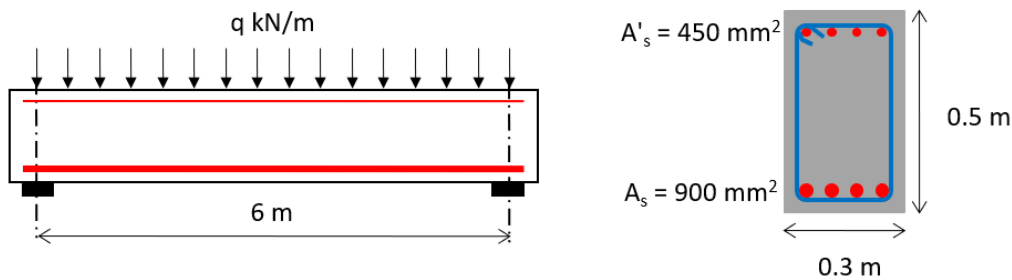


Figure 4. Example studied of reinforced concrete beam.

The values of the effective depth, the modulus of elasticity, the characteristic compressive strength of concrete, and the steel yield stress are  $d=450$  mm,  $E_{cm}=30500$  MPa,  $f_{ck}=25$  MPa and  $f_y=400$  MPa, respectively.

In the original example, the beam was subjected to a uniform load ( $q$ ) that is equal to 16.9 kN/m. The maximum immediate deflection caused by this load, calculated in accordance with ACI-318 [10], is 10.7 mm while the value of the maximum immediate deflection calculated using the simplified method in EN 1992[9] is 9.9 mm. The implicit consideration of shrinkage in the ACI-318 approach justifies this discrepancy. A detailed resolution of these results can be seen on YouTube (in Spanish): ([https://www.youtube.com/watch?v=\\_YInm-fDRXs&t=1037s](https://www.youtube.com/watch?v=_YInm-fDRXs&t=1037s) and <https://www.youtube.com/watch?v=BkXO6s2Ktwk>) for ACI-318 [10] and EN 1992[9], respectively.

### 3. Analytical procedure

As an alternative to the formulations proposed by EN 1992 [9] and ACI-318 [10], an analytical procedure for obtaining the immediate deflections of a reinforced or prestressed concrete element has been applied as follow:

- 1) The equilibrium equations, of both axial forces and bending moments at cross-sectional level, are

$$N = \int_{A_c} \sigma_c (\varepsilon_{cg} + \phi y) dA_c + \sum_j \sigma_{s,j} (\varepsilon_{cg} + \phi y_j) A_{\phi,j} \quad (1 a)$$

$$M = \int_{A_c} \sigma_c (\varepsilon_{cg} + \phi y) y dA_c + \sum_j y_j \sigma_{s,j} (\varepsilon_{cg} + \phi y_j) A_{\phi,j} \quad (1 b)$$

with  $N$  and  $M$  as the external axial force and bending moment, respectively.  $A_c$  is the area of concrete,  $\sigma_c$  is the concrete stress. The plane section hypothesis is assumed (Fig.5), so the strain can be expressed as  $\varepsilon=\varepsilon_{cg}+\phi y$ , where  $\varepsilon_{cg}$  is the strain at the center of gravity (cg),  $\phi$  is the curvature, and  $y$  is the distance to the center of gravity.  $\sigma_{s,j}$  is the stress of the  $j$  bar,  $y_j$  is the distance of the  $j$  bar to the center of gravity, and  $A_{\phi,j}$  is the area of the  $j$  bar.

In the equilibrium equations, the model of concrete used is the short-term model proposed by EN 1992 [9] plus a linear tension stiffening model (see Fig.1 which corresponds to a concrete with a characteristic strength ( $f_{ck}$ ) of 25 MPa. A bilinear steel model with no strain hardening has been adopted.

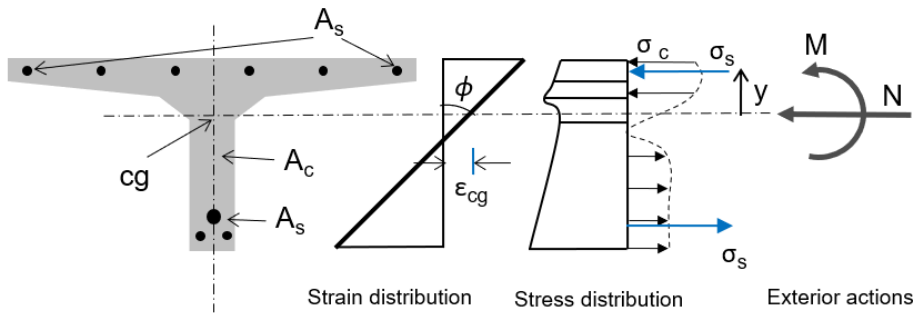


Figure 5. Plane section hypothesis. Stress distribution. External actions.



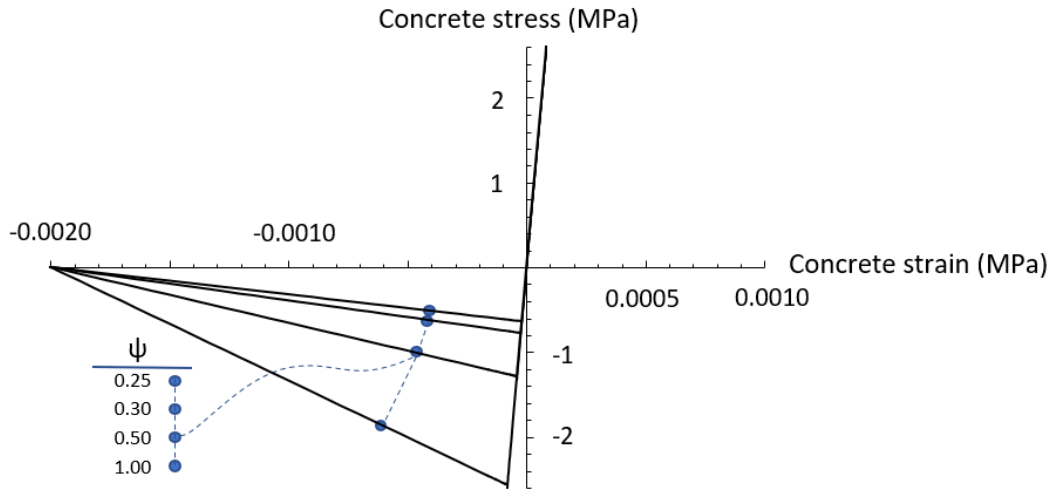


Figure 6. Linear approximations of tensile strength of concrete (tension stiffening)

The moment-curvature diagrams of the cross-section for the different values of  $\psi$  are calculated introducing each one of the linear approximations of the tension stiffening in Fig.6 in the equilibrium equations, see Fig.7.

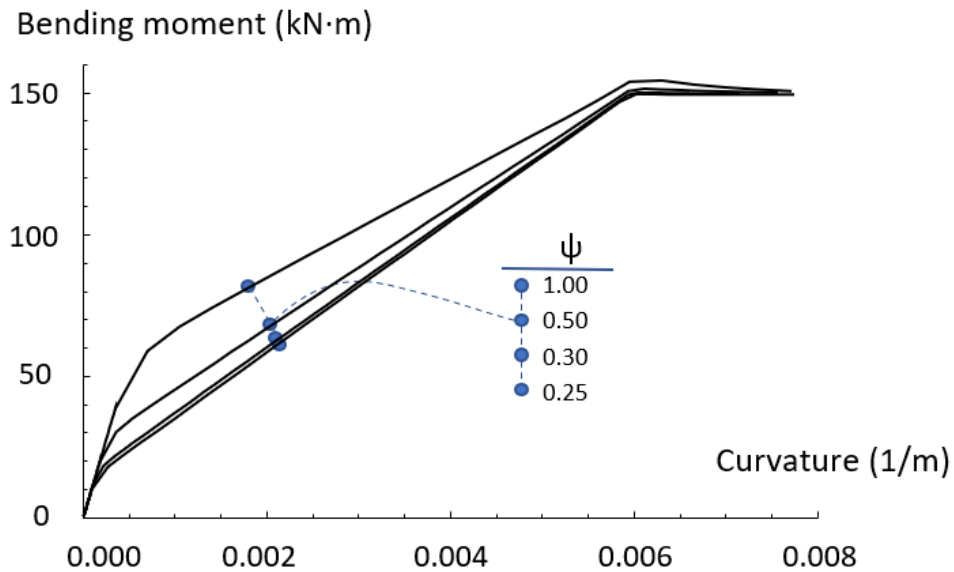


Figure 7. Moment curvature diagrams for the tensile model of concrete in Fig. 6

The theoretical deflection of the beam in Fig.4 is solved by the integration of curvatures using finite-differences. The beam was divided into 20 segments. Table 1 summarized the values obtained for both the moments and curvatures at cracking ( $M_{cr}$  and  $\phi_{cr}$ , respectively) and the maximum deflection ( $\delta_{max}$ ). The computer code is available on request.

Table 1. Maximum deflections

$\Psi$	$M_{cr}$ (kN·m)	$\phi_{cr}$ (1/m)	$\delta_{max}$ (mm)
1.0	38.64	0.00035	4.68
0.5	19.82	0.00018	8.41



0.3	12.08	0.00011	9.70
0.25	9.91	0.00009	10.00

As can be seen in Table 1, the linear approximation (i.e.  $\Psi=1$ ) leads to a maximum deflection of less than half of the deflection predicted by the regulation. By ensuring that the theoretical deflection equals the deflection given by the regulation (EN 1992 [9] in this case) ( $\delta_{\max}=9.9$  mm) a linear interpolation between the two bottom rows results in  $\psi=0.27$ .

The new version of Eurocode 2 (prEN 1992) has reduced the effective area of concrete influenced by tensile stress in concrete, from the traditional value of a square area centered on the reinforcing bar of  $15\Phi$  side to  $10\Phi$  side. This is a variation of the effective concrete area of 44%. Additionally, in order to compensate for the sudden drop in tensile stress for strains greater than those that correspond to the first crack (Fig. 3), given by most of the existing models, a continuous linear function is proposed with a reduction in the tensile capacity of 0.6. If these two values (0.44 and 0.6) are fitted into a single parameter  $\psi$  (i.e.  $0.44 \cdot 0.6=0.26$ ), the result obtained of 0.27 is similar to this value.

#### 4. Conclusions

Due to the relative importance of the tension stiffening phenomenon, for the sake of simplicity, complex expressions of tension stiffening are being substituted with simpler linear approximations. Although linear approximations of tension stiffening lead to more rigid solutions in term of deflections, the simplicity of these approximations means that they are being widely used in computer software.

This work presents a new linear approximation that matches the results given by current standards in terms of deflections and this overcomes the problem caused by underestimating the deflections inherent in bilinear approximations.

#### Conflict of interest

On behalf of all the authors, the corresponding author states that there is no conflict of interest.

#### Data Availability Statement

A computer code has been developed for the development of this paper; the code is available on request from any of the authors .

#### References

- [1] Wu HQ, Gilbert RI. An experimental study of tension stiffening in reinforced concrete members under short-term and long-term loads. Sidney: 2008.
- [2] Vecchio FJ, Collins MP, F.J. Vecchio and M.P. Collins. The Modified Compression-Field Theory for Reinforced Concrete Elements Subjected to Shear. ACI J 1986;83:219–31.
- [3] Hsu T. Softened truss model theory for shear and torsion. ACI Struct J 1988;85:624–35.
- [4] Carbonell-Márquez JF, Gil-Martín LM, Alejandro Fernández-Ruiz M, Hernández-Montes E. Effective area in tension stiffening of reinforced concrete piles subjected to flexure according to Eurocode 2. Eng Struct 2014;76. <https://doi.org/10.1016/j.engstruct.2014.06.041>.

- [5] Bentz EC. Explaining the Riddle of Tension Stiffening Models for Shear Panel Experiments. *J Struct Eng* 2005;131:1422–5. [https://doi.org/10.1061/\(asce\)0733-9445\(2005\)131:9\(1422\)](https://doi.org/10.1061/(asce)0733-9445(2005)131:9(1422)).
- [6] Gil-Martín LM, Hernández-Montes E, Aschheim M, Pantazopoulou SJ. A simpler compression field theory for structural concrete. *Stud e Ric Di Milano Sc Di Spec Costr Cem Armato* 2011;31:11–41.
- [7] McKenna F, Fenves GL, Scott MH. Open system for earthquake engineering simulation 2000.
- [8] SAP2000. [www.csiamerica.com](http://www.csiamerica.com) 2021.
- [9] prEN1992-1-1. Eurocode 2: Design of concrete structures - Part 1–1: General rules and rules for buildings, bridges and civil engineering structures EN 1992-1-1. Brussels: European Committee for Standardization; 2022.
- [10] ACI Committee 318. Building Code Requirements for Structural Concrete. Farmington Hills, MI: 2019.
- [11] CEB. CEB Design Manual on Cracking and deformations. 1983. Comité Euro-International du Béton. 1983.
- [12] Lee SC, Cho JY, Vecchio FJ. Model for post-yield tension stiffening and rebar rupture in concrete members. *Eng Struct* 2011;33:1723–33. <https://doi.org/10.1016/j.engstruct.2011.02.009>.
- [13] Bischoff PH. Revaluation of Deflection Prediction for Concrete Beams Reinforced with Steel and Fiber Reinforced Polymer Bars. *J Struct Eng* 2005;131:752–67. [https://doi.org/10.1061/\(ASCE\)0733-9445\(2005\)131:5\(752\)](https://doi.org/10.1061/(ASCE)0733-9445(2005)131:5(752)).
- [14] Marí A, Torres L, Oller E, Barris C. Performance-based slenderness limits for deformations and reinforcement stresses control in reinforced concrete beams. *Hormigón y Acero* 2021;72:31–7. <https://doi.org/10.33586/hya.2020.2112>.